

The Effect of Cutting Fluid on Chip-Tool Interface Temperature While Turning AISI 4340 Steel

E. Vijayakumar^{1*}, Milon D.Selvam², K. Prasath³

¹PG Scholar, Department of Mechanical Engineering, Karpagam Academy of Higher Education, Coimbatore-641021, India

^{2,3}Assistant Professor, Department of Mechanical Engineering, Karpagam Academy of Higher Education, Coimbatore-641021, India

Original Research Article

*Corresponding author

E. Vijayakumar

Article History

Received: 20.01.2018

Accepted: 10.02.2018

Published: 15.02.2018

DOI:

10.21276/sjet.2018.6.2.2



Abstract: The machining parameters of any machining operation highly affect the surface quality of a component. The objective of this paper is to study the effect of cutting fluid (SERVOCUT 'S' Grade oil emulsified with water) on chip-tool interface temperature while turning AISI 4340 cylindrical steel components. The turning operation was carried out with TiN coated carbide insert on the AISI 4340 steel under traditionally flooded condition. The turning parameters, namely cutting velocity, feed rate and depth of cut were chosen for the conduct of experiments. The chip-tool interface temperature of the turned specimens was measured using a properly calibrated K-type thermocouple.

Keywords: AISI 4340, TiN coated carbide insert, turning operation, flooded condition, chip-tool interface temperature.

INTRODUCTION

Machining is one of the most versatile manufacturing processes for producing desired shape and size of a component for the functional behaviour of any machine mechanism [1-3]. Manufacturing involves numerous processes to convert raw materials to finished products to be used for various purposes [3-4]. The poor surface quality fails to satisfy functional requirements of the products, while extremely high surface quality causes high production costs and low overall productivity. Hence, the improved surface quality and the economics of the manufacturing operation are becoming a very important consideration to produce the finished products [1-3, 5-6]. The cutting fluids are employed in machining to decrease friction, cool the job and wash away the chips.

With the application of cutting fluids, the wear rate of the tool gets reduced and surface quality of machined components gets improved. In addition, the cutting fluids protect the machined surface from the occurrence of corrosion. They also minimize the cutting forces thus saving the energy. Many researchers are working in the field of cutting fluids to reduce its usage while machining for environmental and economic benefits [7-11].

Tool wear can be minimized by employing lower values of cutting velocity, feed rate, depth of cut and machining time [12]. The machining power and cutting tool wear increase almost linearly with the increase of cutting speed and feed rate [13-14]. In high-speed machining of stainless steel using coated carbide tool, the feed rate is found to be more significant followed by the cutting speed and the depth of cut [15-18].

The researchers [19] studied the influence of turning parameters such as speed, feed rate, depth of cut

and tool nose radius on the surface roughness of medium carbon steel and suggested optimized parametric setting for obtaining better surface finish and lesser heat at the machining zone.

From the literature survey, it becomes clear that the effect of cutting fluids in the field of machining carbon steels have been investigated by many researchers. Still, there remains some difficulty in the machining of carbon steel with the application of cutting fluids, which reveals that still more research has to be carried out to find a reasonable solution. Therefore, the turning operation was carried out on the AISI 4340 steel under flooded machining conditions in order to study the effect of cutting fluid on the chip-tool interface temperature of the turned specimens in this study.

Experimental conditions

- Workpiece used – AISI 4340 (Ø80mm x 150mm)
- Cutting tool used – TiN Coated carbide insert

- Machine tool – Turning centre (All Geared Conventional Lathe)
- Cutting fluid – Mineral based (Servocut ‘S’) emulsion
- Coolant application technique – flooded
- Output response – Chip-tool interface temperature

RESULTS AND DISCUSSION

The parameters namely cutting velocity (m/min), feed rate (mm/rev) and depth of cut (mm) were considered while turning of AISI 4340 steel under flood, near dry and dry machining conditions. The various levels of the parameters are given in Table 1.

Table-1: Parameters and their levels

Parameter	Notation	Levels		
		1	2	3
Cutting velocity (m/min)	v	325	350	375
Feed rate (mm/rev)	f	0.1	0.15	0.2
Depth of Cut (mm)	d	0.3	0.6	0.9

Effect of Parameters

The effect of cutting velocity was observed with a constant feed rate of 0.15 mm/rev and with a constant depth of cut of 0.6 mm while machining steel

AISI 4340. It was observed from Figure 1, that the chip-tool interface temperature value increased drastically with the increase of cutting velocity.

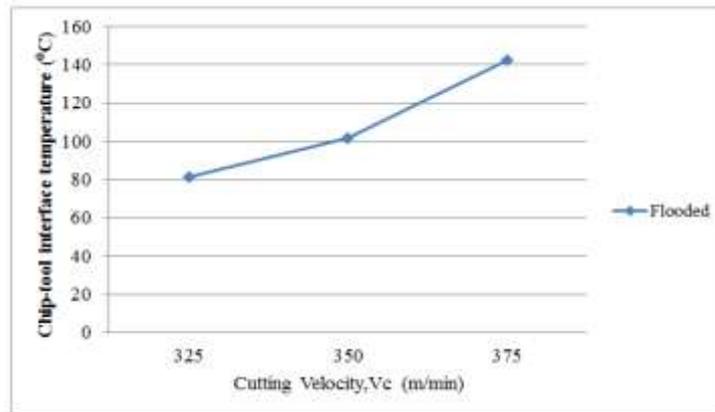


Fig-1: Effect of cutting velocity on chip-tool interface temperature

The effect of feed rate was observed with a constant cutting velocity of 350 m/min and with a constant depth of cut of 0.6 mm while machining steel

AISI 4340. It was observed from Figure 2, that the chip-tool interface temperature value increased gradually with the increase of feed rate.

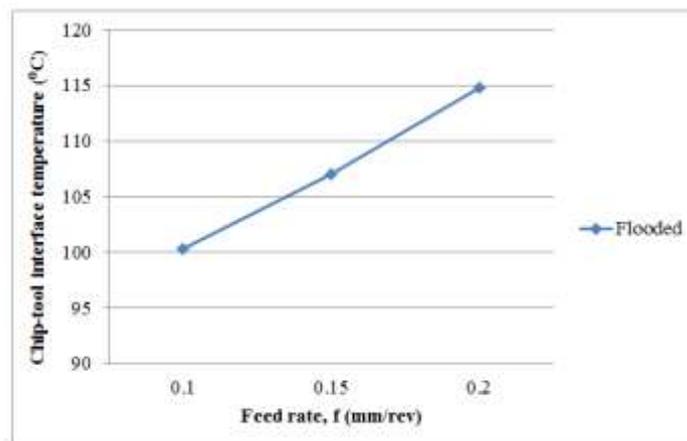


Fig-2: Effect of cutting feed on chip-tool interface temperature

The effect of depth of cut was studied with a constant cutting velocity of 350 m/min and with a constant feed rate of 0.15 mm/rev when machining steel

AISI 4340. It was observed from Figure 3, that, the chip-tool interface temperature value increased gradually with the increase of depth of cut.

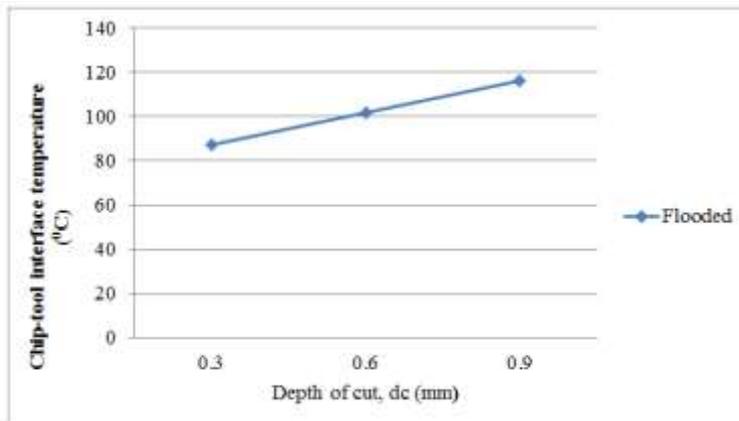


Fig-3: Effect of depth of cut on chip-tool interface temperature

Contribution of Parameters

The machining parameters were ranked based on the variation of their effect on the chip-tool interface

temperature. The percentage contribution of machining parameters is shown in Figure 4.

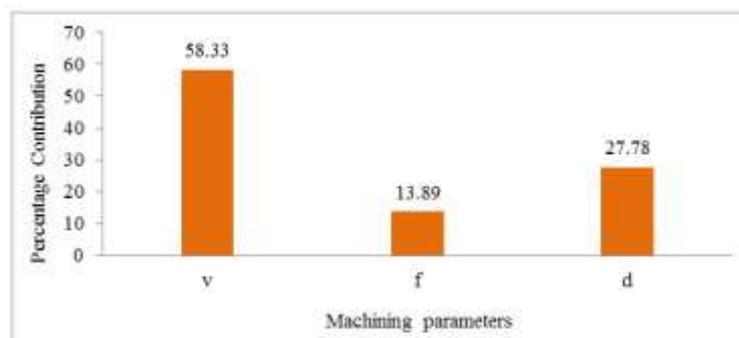


Fig-4: Percentage contribution

CONCLUSION

Based on the chip-tool interface temperature test conducted on AISI 4340 steel during turning operation with titanium nitride coated carbide insert under flooded machining condition, this research work is concluded with the following key points:

- From the effect curve plotted for cutting velocity, it was evident, that the chip-tool interface temperature value increased drastically with the increase of cutting velocity.
- From the effect curve plotted for feed rate, it was evident, that the chip-tool interface temperature value increased gradually with the increase of feed rate.
- From the effect curve plotted for depth of cut, it was evident, that the chip-tool interface temperature value increased gradually with the increase of depth of cut.
- From the experimentation, it could be concluded that cutting velocity has a greater effect on the chip-tool interface temperature followed by the depth of cut and feed rate, which is shown in the contribution chart (Figure 4).

REFERENCES

1. Ozcelik B, Kuram E, Cetin MH, Demirbas E. Experimental investigations of vegetable based cutting fluids with extreme pressure during turning of AISI 304L. *Tribology International*. 2011 Nov 1;44(12):1864-71.
2. Leppert T. Effect of cooling and lubrication conditions on surface topography and turning process of C45 steel. *International Journal of Machine Tools and Manufacture*. 2011 Feb 1;51(2):120-6.
3. Islam MN, Anggono JM, Pramanik A, Boswell B. Effect of cooling methods on dimensional accuracy and surface finish of a turned titanium part. *The International Journal of Advanced Manufacturing Technology*. 2013 Dec 1;69(9-12):2711-22.
4. Selvam MD, Dawood DA, Karuppusami DG. Optimization of machining parameters for face milling operation in a vertical CNC milling machine using genetic algorithm. *IRACST-Engineering Science and Technology: An International Journal (ESTIJ)*. 2012 Aug;2(4).
5. Leppert T. „Influence of cooling and lubrication on selected features of geometrical structure of surfaces turned at high cutting speeds”. *Journal of Polish CIMAC*. 2012;7(3):121-6.

6. Suresh R, Basavarajappa S, Samuel GL. Some studies on hard turning of AISI 4340 steel using multilayer coated carbide tool. *Measurement*. 2012 Aug 1;45(7):1872-84.
7. Selvam MD, Srinivasan V, Sekar CB. An Attempt To Minimize Lubricants In Various Metal Cutting Processes. *International Journal of Applied Engineering Research*. 2014;9(22):7688-92.
8. Suresh R, Basavarajappa S, Gaitonde VN, Samuel GL. Machinability investigations on hardened AISI 4340 steel using coated carbide insert. *International Journal of Refractory Metals and Hard Materials*. 2012 Jul 1;33:75-86.
9. Hamdan A, Sarhan AA, Hamdi M. An optimization method of the machining parameters in high-speed machining of stainless steel using coated carbide tool for best surface finish. *The International Journal of Advanced Manufacturing Technology*. 2012 Jan 1;58(1-4):81-91.
10. Selvam MD, Sivaram NM. Optimal Parameter Design by Taguchi Method for Mechanical Properties of Al6061 Hybrid Composite Reinforced With Fly Ash/Graphite/Copper.
11. Prasath K, Prasanna R and Milon D. Selvam. Optimization of Process Parameters in Wire Cut EDM of Mild Steel and Stainless Steel using robust design, *International Journal of ChemTech Research*. 2018; Vol.11, No.01, pp. 83-91.
12. Balakumar S, Selvam MD, Nelson AJ. Wear and Friction Characteristics of Aluminium Matrix Composites Reinforced With Flyash/Cu/Gr Particles.
13. Selvam MD, Senthil P, Sivaram NM. Parametric optimisation for surface roughness of AISI 4340 steel during turning under near dry machining condition. *International Journal of Machining and Machinability of Materials*. 2017;19(6):554-69.
14. Selvam Md, Sivaram N. The Effectiveness Of Various Cutting Fluids On The Surface Roughness Of Aisi 1045 Steel During Turning Operation Using Minimum Quantity Lubrication System. *Journal on Future Engineering & Technology*. 2017 Aug 1;13(1).
15. Yogi KS. An empirical and fuzzy logic approach to product quality and purchase intention of customers in two wheelers. *Pacific Science Review B: Humanities and Social Sciences*. 2015 Jan 1;1(1):57-69.
16. Walker T. *A guide to machining with Minimum Quantity Lubrication*, Unist, Inc. 2015.
17. Le Coz G, Marinescu M, Devillez A, Dudzinski D, Velnom L. Measuring temperature of rotating cutting tools: Application to MQL drilling and dry milling of aerospace alloys. *Applied Thermal Engineering*. 2012 Apr 1;36:434-41.
18. Hamdan A, Sarhan AA, Hamdi M. An optimization method of the machining parameters in high-speed machining of stainless steel using coated carbide tool for best surface finish. *The International Journal of Advanced Manufacturing Technology*. 2012 Jan 1;58(1-4):81-91.
19. Selvam MD, Senthil P. Investigation on the effect of turning operation on surface roughness of hardened C45 carbon steel. *Australian Journal of Mechanical Engineering*. 2016 May 3;14(2):131-7.